



杭州中晶电子科技有限公司

HangZhou FreqControl Electronic Technology Ltd

1106, Crystal International Business Center(CIBC), No.198 Wuxing Rd ,Qianjiang new city Hangzhou,

P.R.China Post code: 310006

Tel: 0086- 571- 85803723 85803731 85803732

Fax: 0086-571-85803724

E-mail: sales@cqtgroup.com thwu@mail.hz.zj.cn

<http://www.csimc-freqcontrol.com> <http://www.cqtgroup.com>

Different Properties			
Parameter Value	JGS1	JGS2	JGS3
Maximum Size	<Φ200mm	<Φ300mm	<Φ200mm
Transmission Range (Medium transmission ratio)	0.17~2.10um (Tavg>90%)	0.26~2.10um (Tavg>85%)	0.185~3.50um (Tavg>85%)
OH- Content	1200 ppm	150 ppm	5 ppm
Fluorescence (ex 254nm)	Virtually Free	Strong v-b	Strong V-B
Impurity Content	5 ppm	20-40 ppm	40-50 ppm
Birefringence Constant	2-4 nm/cm	4-6 nm/cm	4-10 nm/cm
Melting Method	Synthetic CVD	Oxy-hydrogen melting	Electrical melting
Applications	Laser substrate: Window, lens, prism, mirror...	Semiconductor and high temperature window	IR & UV substrate

Same properties			
Density		2.20g/cm ³	
Abbe Constant		67.6	
Refractive Index (nd) at 588nm		1.4586	
Wavelength (um)	Refractive Index (n)	Wavelength (um)	Refractive Index (n)
0.200	1.55051	1.000	1.45042
0.220	1.52845	1.064	1.44962
0.250	1.50745	1.100	1.44920
0.300	1.48779	1.200	1.44805
0.320	1.48274	1.300	1.44692
0.360	1.47529	1.500	1.44462
0.400	1.47012	1.600	1.44342
0.450	1.46557	1.700	1.44217
0.488	1.46302	1.800	1.44087
0.500	1.46233	1.900	1.43951
0.550	1.46008	2.000	1.43809
0.588	1.45860	2.200	1.43501
0.600	1.45804	2.400	1.43163
0.633	1.45702	2.600	1.42789
0.650	1.45653	2.800	1.42377
0.700	1.45529	3.000	1.41925
0.750	1.45424	3.200	1.41427
0.800	1.45332	3.370	1.40990

Save a tree. Don't print this paper unless it's really necessary

杭州市钱江新城五星路 198 号瑞晶国际商务中心 1106 室 邮编 310006

电话: 0086-571-85803723 85803731 85803732 传真: 0086-571-85803724



杭州中晶电子科技有限公司

HangZhou FreqControl Electronic Technology Ltd

1106, Crystal International Business Center(CIBC), No.198 Wuxing Rd ,Qianjiang new city Hangzhou,

P.R.China Post code: 310006

Tel: 0086- 571- 85803723 85803731 85803732

Fax: 0086-571-85803724

E-mail: sales@cqtgroup.com thwu@mail.hz.zj.cn

[Http://www.csimc-freqcontrol.com](http://www.csimc-freqcontrol.com) [Http://www.cqtgroup.com](http://www.cqtgroup.com)

0.850	1.45250	3.507	1.40566
0.900	1.45175	3.707	1.39936

Hardness	5.5 - 6.5 Mohs' Scale 570 KHN 100
Design Tensile Strength	4.8×10^7 Pa (N/mm ²) (7000 psi)
Design Compressive Strength	Greater than 1.1×10^9 Pa (160,000 psi)
Bulk Modulus	3.7×10^{10} Pa (5.3×10^6 psi)
Rigidity Modulus	3.1×10^{10} Pa (4.5×10^6 psi)
Young's Modulus	7.2×10^{10} Pa (10.5×10^6 psi)
Poisson's Ratio	0.17
Coefficient of Thermal Expansion	5.5×10^{-7} cm/cm.°C (20°C-320°C)
Thermal Conductivity	1.4 W/m.°C
Specific Heat	670 J/kg.°C
Softening Point	1683°C
Annealing Point	1215°C
Strain Point	1120°C
Electrical Receptivity	7×10^7 ohm.cm (350°C)
Dielectric Properties (20°C and 1 MHz)	
Constant	3.75
Strength	5×10^7 V/m
Loss Factor	Less than 4×10^{-4}
Dissipation Factor	Less than 1×10^{-4}
Velocity of Sound-Shear Wave	3.75×10^3 m/s
Velocity of Sound/Compression Wave	5.90×10^3 m/s
Sonic Attenuation	Less than 11 db/m MHz
Permeability Constants (cm ³ mm/cm ² sec cm of Hg)	
Helium	(700°C) 210×10^{-10}
Hydrogen	21×10^{-10}
Deuterium	17×10^{-10}
Neon	9.5×10^{-17}
Chemical Stability (except hydrofluoric)	High resistance to water and acids

Save a tree. Don't print this paper unless it's really necessary

杭州市钱江新城五星路 198 号瑞晶国际商务中心 1106 室 邮编 310006

电话: 0086-571-85803723 85803731 85803732 传真: 0086-571-85803724



杭州中晶电子科技有限公司

HangZhou FreqControl Electronic Technology Ltd

1106, Crystal International Business Center(CIBC), No.198 Wuxing Rd ,Qianjiang new city Hangzhou,

P.R.China Post code: 310006

Tel: 0086- 571- 85803723 85803731 85803732

Fax: 0086-571-85803724


E-mail: sales@cqtgroup.com thwu@mail.hz.zj.cn

[Http://www.csimc-freqcontrol.com](http://www.csimc-freqcontrol.com) [Http://www.cqtgroup.com](http://www.cqtgroup.com)


Transmission Curve

See below


Ultraviolet Grade Fused Silica (JGS1)

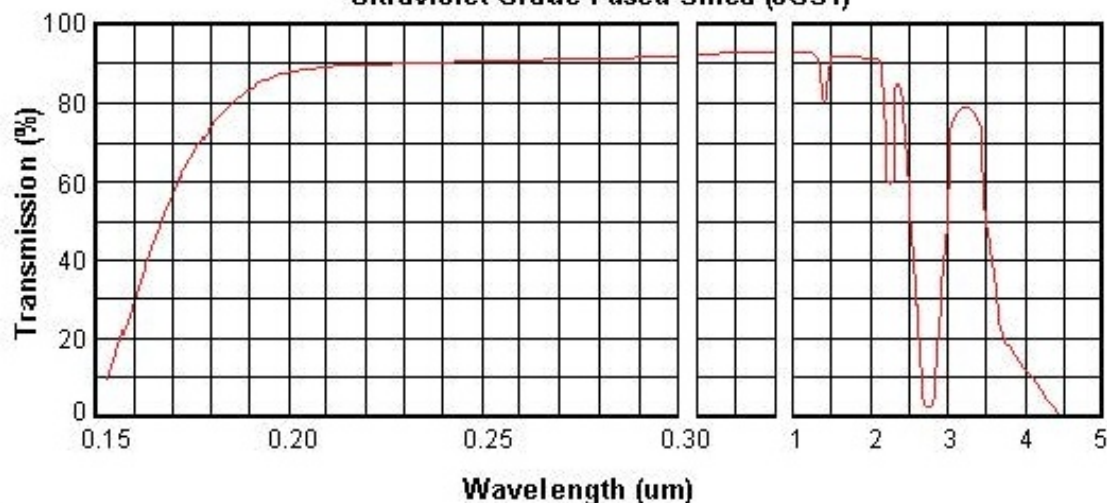

Optical Grade Fused Quartz (JGS2)

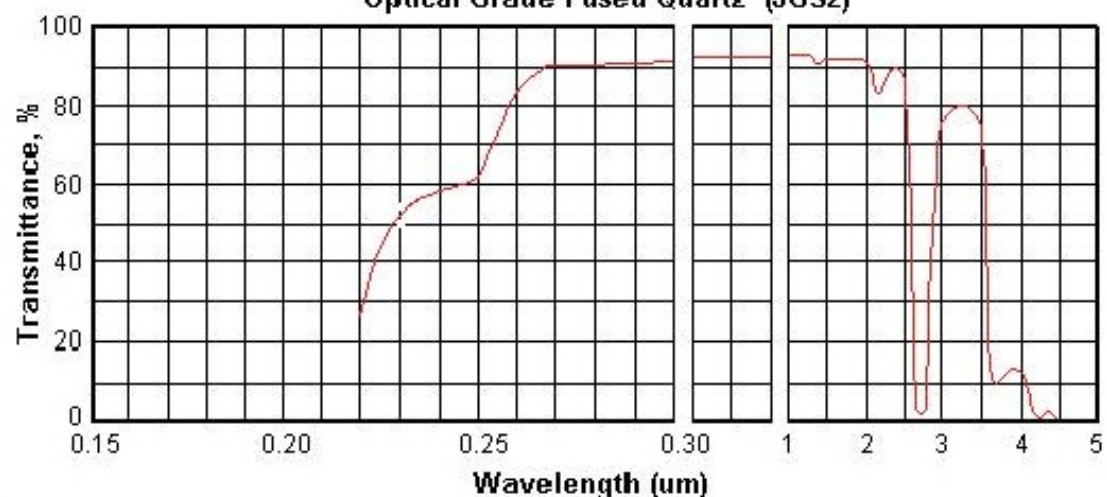

Full Spectrum Fused Silica (JGS3)

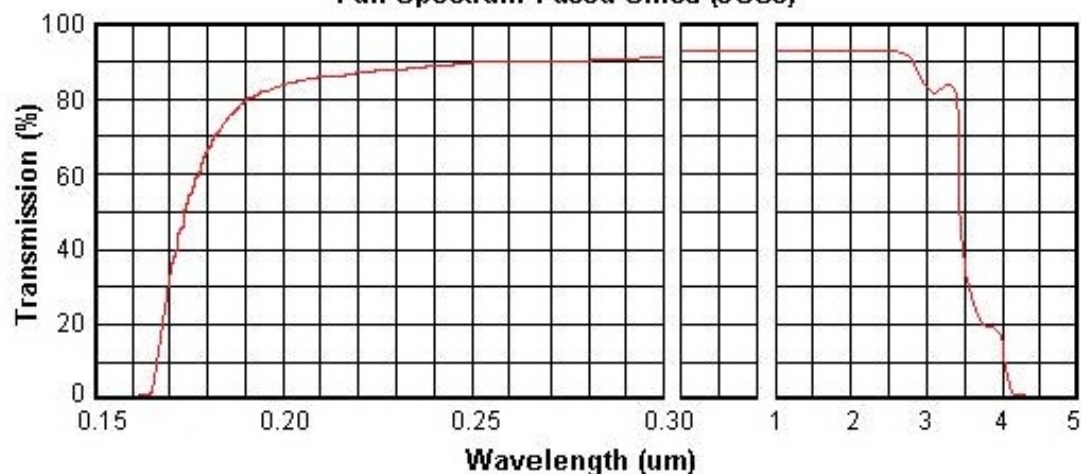

Save a tree. Don't print this paper unless it's really necessary

杭州市钱江新城五星路 198 号瑞晶国际商务中心 1106 室 邮编 310006

电话: 0086-571-85803723 85803731 85803732 传真: 0086-571-85803724